



Effect of competing solutes on arsenic(V) adsorption using iron and aluminum oxides

Youngran Jeong^{1,2}, FAN Maohong^{1,2,*}, Johannes Van Leeuwen¹, Joshua F. Belczyk³

1. Department of Civil, Construction and Environmental Engineering, Iowa State University, Ames, IA 50011, USA. E-mail: mfan@iastate.edu

2. Center for Sustainable Environmental Technology, Iowa State University, Ames, IA 50011, USA

3. Bailey PVS, Canonsburg, PA 15317, USA

Received 9 October 2006; revised 5 December 2006; accepted 26 March 2007

Abstract

The study focused on the effect of several typical competing solutes on removal of arsenic with Fe_2O_3 and Al_2O_3 . The test results indicate that chloride, nitrate and sulfate did not have detectable effects, and that selenium(IV) (Se(IV)) and vanadium(V) (V(V)) showed slight effects on the adsorption of As(V) with Fe_2O_3 . The results also showed that adsorption of As(V) on Al_2O_3 was not affected by chloride and nitrate anions, but slightly by Se(IV) and V(V) ions. Unlike the adsorption of As(V) with Fe_2O_3 , that with Fe_2O_3 was affected by the presence of sulfate in water solutions. Both phosphate and silica have significant adverse effects on the adsorption of As(V) adsorption with Fe_2O_3 and Al_2O_3 . Compared to the other tested anions, phosphate anion was found to be the most prominent solute affecting the As(V) adsorption with Fe_2O_3 and Al_2O_3 . In general, Fe_2O_3 has a better performance than Al_2O_3 in removal of As(V) within a water environment where multi competing solutes are present.

Key words: adsorption; arsenic; iron oxide; aluminum oxide; sulfate; selenium(IV); vanadium(V); phosphate; silica

Introduction

Arsenic (As) is well known as a useful compound in industrial applications such as smelting, agricultural pesticides and insecticides (LANL, 2004). However, As has also been considered as a strong poisonous chemical due to its odorless and nearly tasteless nature (Buchanan, 1962; Ferguson and Gavis, 1972). Even small amounts of arsenic in drinking water can have adverse effects on human health. Known consequences include cardiovascular diseases, conjunctivitis, and skin cancer (Tseng *et al.*, 1968; Klaassen, 1996; Zhang *et al.*, 2004; Safiullah *et al.*, 2004; Yean *et al.*, 2005; Zhang and Stanforth, 2005). Of organic and inorganic arsenic, inorganic arsenic commonly exists in two valence states, As(III) and As(V), in groundwater or surface water (Ferguson and Gavis, 1972; Reynolds *et al.*, 1999). Inorganic arsenic also has adverse effects on human health. As(III) effects on human health are more adverse than those of As(V); however, it is easy to transform As(III) easily to As(V) in oxygenated environments (Brookins, 1988). In addition, the efficiency of removal of As(V) by mineral oxides is found to be greater than that of As(III). Therefore, the preoxidation of As(III) to As(V) by using oxidizing agents including oxygen and ozone, prior to adsorption is recommended (Oscarson *et al.*, 1983; Frank and Clifford, 1986).

Due to the serious effects of arsenic on people's health,

World Health Organization (WHO) recommended 10 $\mu\text{g/L}$ as the guideline value for arsenic in drinking water in 2001 (WHO, 2001) and the U.S. Environmental Protection Agency (USEPA) also promulgated 10 $\mu\text{g/L}$ as its new arsenic standard for drinking water (USEPA, 2001a). Therefore, development of various arsenic removal technologies is important. Metal oxides have been studied by many researchers as one of the most promising arsenic removal technologies. These materials include amorphous ferric hydroxide (Pierce and Moore, 1982), granular ferric hydroxide (GFH) (Thirunavukkarasu *et al.*, 2003), amorphous aluminum oxide (Anderson *et al.*, 1976), and activated alumina (Rosenblum and Clifford, 1983). Our previous research has shown that Fe_2O_3 and Al_2O_3 are good adsorption media (Jeong *et al.*, 2005) for As(V) without the presence of competing solutes. It was observed that their arsenate adsorption capacities varied with the pH values of As(V) solutions, and the highest adsorption of As(V) on both Fe_2O_3 and Al_2O_3 was observed at pH 6.

However, some soluble solutes in water are often present in groundwater and surface water (Meng *et al.*, 2002; Roberts *et al.*, 2004; Hug *et al.*, 2005). Welch *et al.* (1998) reported that the phosphate (as P) in the shallow groundwater from the southern Carson Desert in the United States is higher than 4 mg/L. Many studies have indicated that the competing solutes affect the removal of As(V) by adsorbents. The presence of phosphate resulted in a severe reduction in arsenate adsorption by ferrihy-

*Corresponding author. E-mail: mfan@iastate.edu.

drite (Jain and Loeppert, 2000), goethite (α -FeOOH) and gibbsite (γ -Al(OH)₃) (Manning and Goldberg, 1996b), kaolinite (Al₂Si₂O₅(OH)₄), montmorillonite ((Na, Ca)(Al, Mg)₆(Si₄O₁₀)₃(OH)_{6-n}H₂O), and illite ((K, H₃O)(Al, Mg, Fe)₂(Si, Al)₄O₁₀(OH)₂, (H₂O)) (Manning and Goldberg, 1996a). The high concentration of sulfate reduced the removal of arsenate on alumina and hydrous ferric oxide, although the competing effect of sulfate anions was of a lower degree than that of phosphate anions (Wilkie and Hering, 1996; Xu *et al.*, 1988). Meng *et al.* (2000) showed that the removal of As(V) by coprecipitation and adsorption with ferric chloride was moderately affected due to the presence of silicate. Lee *et al.* (2004) discovered that 35.5 mg/L of silica and 13 μ g/L of V(V) in groundwater had an unfavorable impact on As(V) adsorption using GFH. Davis and Misra (1997) found that Se(IV) could be a competing solute in the adsorption of As(V) onto aluminum-based oxides.

This research studied the competitive effect of co-occurring solutes on the adsorption of As(V) with Fe₂O₃ and Al₂O₃, including chloride, nitrate, sulfate, phosphate, silicate, Se(IV) and V(V). It is expected that the research will provide more information for actually applying Fe₂O₃ and Al₂O₃ in the removal of As(V) in water treatment industry.

1 Materials and methods

1.1 Preparation of adsorbents and solutions

Iron oxide (Fe₂O₃-PVS; physical vapor synthesis, Bailey-PVS, USA) and aluminum oxide (Al₂O₃-ALO101, Praxair, USA), as mentioned in a previous paper (Jeong *et al.*, 2005), were used in our experiments for studying the competing effects of solutes on the adsorption of As(V). These oxides, Fe₂O₃ and Al₂O₃, are nonporous adsorbents with low specific surface areas (5.05 and 0.55 m²/g) and were used in our experiments without further purification.

Chemicals including NaCl, NaNO₃, Na₂SO₄, Na₂HPO₄, Na₂SiO₃·9H₂O, and V₂O₅ were reagent grade materials from Fisher Chemicals (USA). Sodium arsenate (Na₂HAsO₄·7H₂O) and sodium selenite (Na₂SeO₃) were purchased from Matheson Coleman and Bell (Norwood, Ohio, USA) and from Sigma-Aldrich (USA), respectively. Stock solutions of arsenate (HAsO₄²⁻, 10 mg/L), chloride (Cl⁻, 1 g/L), sulfate (SO₄²⁻, 1 g/L), nitrate as nitrogen (NO₃⁻-N, 1 g/L), phosphate (HPO₄²⁻, 1 g/L), silica (SiO₃²⁻, 1 g/L), vanadium as vanadate (V⁵⁺, 5 mg/L), and selenium as selenite ion (SeO₃²⁻, 5 mg/L) were prepared by dissolving the respective chemicals in deionized water. All of these solutions, with the exception of the silica solution, were further diluted to suitable concentrations on the day of use. Silica stock solution was prepared every week and rapidly mixed with arsenate-contaminated water to maintain the main silicate species found in natural aquatic systems (monomeric H₄SiO₄); the quick dilution was used to avoid the formation of silicate polymers (Stumm and Morgan, 1996; Roberts *et al.*, 2004).

1.2 Batch experiment

Batch experiments were performed in a jar tester (PB-700TM, Phipps & Bird, USA) having six jars each of 2 L volume and six two-paddle stirrers to study the effect of competing ions on the adsorption of As(V) by Fe₂O₃ and Al₂O₃. The tested initial As(V) concentration was 200 μ g/L (2.67×10^{-6} mol/L), and the dosages of Fe₂O₃ and Al₂O₃ varied in the ranges of 0.05–1 g/L and 0.5–6 g/L, respectively. Each of the competing solutes was separately added into water samples. Amounts of solutes added in the water samples were based on the typical concentrations of solutes in the natural water bodies (Meng *et al.*, 2002; US EPA, 2001b; APHA, 1999; Heinz Center, 2000). Generally, the concentrations of sulfate and chloride were much higher than those of nitrate and silica in the water. The concentrations of phosphate, V(V) and Se(IV) were usually lower than 1 mg/L in ground or surface water. The pH values of the test solutions were adjusted to 6 ± 0.1 using either diluted 0.1 mol/L hydrochloric acid (HCl) or 0.1 mol/L sodium hydroxide (NaOH) solutions before adsorption. No buffer was used to keep the pH value of each tested As(V) solution as a constant during each adsorption process because it is impractical to control pH by using a buffer in the real water treatment industry. To avoid the interference of other ions, all glassware was cleaned by soaking in 0.1 mol/L HNO₃ and 0.5 mol/L HCl and rinsed four times with deionized water. In order to avoid the effect of silica of glass beakers, polyethylene beakers were used in the experiments by following standard jar test methods (APHA, 1999). No competing anions on the walls of jars were detected through blank experiments. At room temperature ($25 \pm 0.5^\circ\text{C}$), As(V) adsorption onto Fe₂O₃ and Al₂O₃ with competing solutes was conducted with a stirring rate of 130 ± 5 RPM for 1 h and 2 h, respectively. To analyze the concentrations of As(V) in water after adsorption, supernatant of water samples was collected from the jar using a 10-ml disposable syringe. The samples were filtered through 0.45 μ m syringe filters (Millipore Millex) and analyzed for the concentrations of arsenic and competing anions. The As(V) adsorption uptakes were the difference between the initial and the equilibrium concentrations of As(V) in water. The experiments were performed in triplicate and the mean values were accepted.

1.3 Analytical methods of arsenate and solutes

Arsenate (As(V)), vanadium (V(V)), and selenium (Se(IV)) concentrations in all the samples were measured by inductively coupled plasma-mass spectrometry (ICP-MS, 4500 Series, Hewlett Packard (HP)) following Standard Methods (APHA, 1999). Because high concentrations of chloride interfere in measuring As(V), the interference correction equation provided by HP was applied to identify and measure arsenic concentrations. The analysis of phosphate (HPO₄²⁻ as total P) was also performed using ICP-MS (Dixit and Hering, 2003). The detection limits of ICP-MS were 0.1 μ g/L for arsenic, and 1 μ g/L for phosphate, V(V), and Se(IV), respectively. The measurements were considered as reasonable data in cases

of less than 10% relative standard deviation (RSD) for 0–50 $\mu\text{g/L}$ solute concentrations and the RSD was $\pm 5\%$ in the range of 50–600 $\mu\text{g/L}$ solute concentrations.

The analyses of anions, including nitrate (NO_3^- -N), sulfate (SO_4^{2-}), and chloride (Cl^-), were conducted in our laboratory using an ion chromatograph (IC-DX-120, Dionex) equipped with a Dionex Ion Pac As14 (4 mm \times 250 mm) column and conductivity detection. The eluent solution used for ion chromatography (IC) was $\text{Na}_2\text{CO}_3/\text{NaHCO}_3$ (3.5 mmol/L:1 mmol/L). The molybdosilicate method was used for detecting silica concentrations (APHA, 1999). The concentration of silica was analyzed using a UV visible spectrophotometer (DMS 100, Varian) with a 1-cm light path at a 410-nm wavelength. The detection limit for silica was 1 mg/L. The digestion with NaHCO_3 was not used for checking the existence of molybdate-unreactive silica. Prior to each analysis, standard solutions of each solute were prepared by diluting stock solutions of each solute solution with deionized water.

2 Results and discussion

Fig.1 shows the As(V) removal efficiencies of 0.5 g/L of Fe_2O_3 and 4 g/L of Al_2O_3 with the presence of high concentrations of competing solutes including

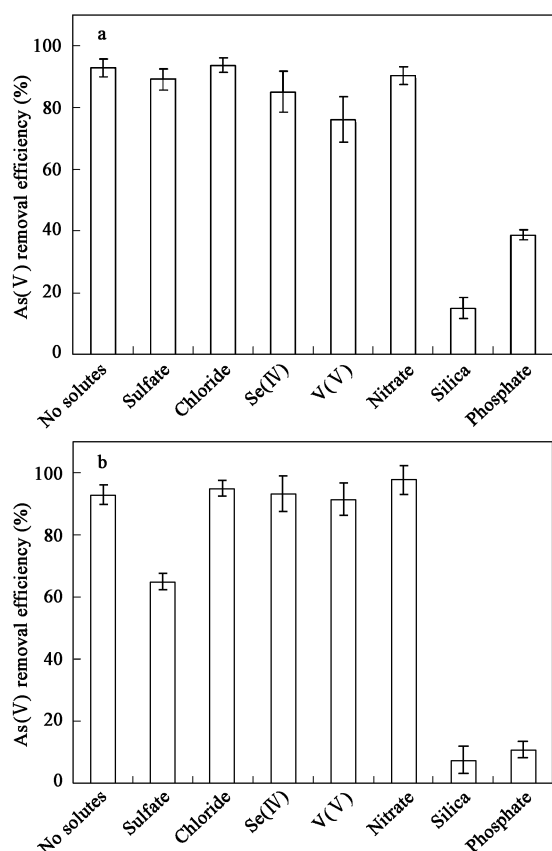


Fig. 1 Effects of various competing solutes on As(V) removal efficiency using Fe_2O_3 (a) and Al_2O_3 (b). Initial As(V) concentration 200 $\mu\text{g/L}$; sulfate and chloride 500 mg/L for each; Se(IV) and V(V) 100 $\mu\text{g/L}$ for each; nitrate 20 mg/L; silica 10 mg/L; phosphate 1000 $\mu\text{g/L}$; pH 6 ± 0.1 . Dosage, 0.5 g/L (a); 4.0 g/L (b).

sulfate (SO_4^{2-}), chloride (Cl^-), nitrate (NO_3^- -N), vanadium (V), selenium (IV), silica (SiO_3^{2-}), and phosphate (HPO_4^{2-}) when the initial As(V) concentrations and pH of water solutions were 200 $\mu\text{g/L}$ and 6 ± 0.1 , respectively. Fig.1a shows that when the dosage of Fe_2O_3 is 0.5 g/L, chloride, nitrate, and sulfate solutes hardly affected the As(V) removal efficiencies, while V(V) and Se(IV) slightly affected the As(V) adsorption and silica and phosphate ions significantly decreased As(V) removal efficiencies. Fig.1b shows that at 4 g/L dosage of Al_2O_3 , chloride, nitrate, V(V), and Se(IV) solutes have little effect on the As(V) removal efficiencies; sulfate ions moderately reduced As(V) removal efficiencies; silica and phosphate ions significantly decreased As(V) removal efficiencies.

2.1 Chloride and nitrate

As shown in Figs.1a and 1b, the adsorption of As(V) on Fe_2O_3 and Al_2O_3 was found to be independent of the concentration of chloride and nitrate at pH 6. We observed that the concentrations of these ions remained the same after adsorption processes. This finding is consistent with that reported by Xu *et al.* (2002) when they used aluminum-loaded shirasu-zeolite for removal of As(V). This observation can be attributed to the fact that complexes of chloride and nitrate with Fe_2O_3 or Al_2O_3 are much weaker than those between arsenate and Fe_2O_3 or Al_2O_3 .

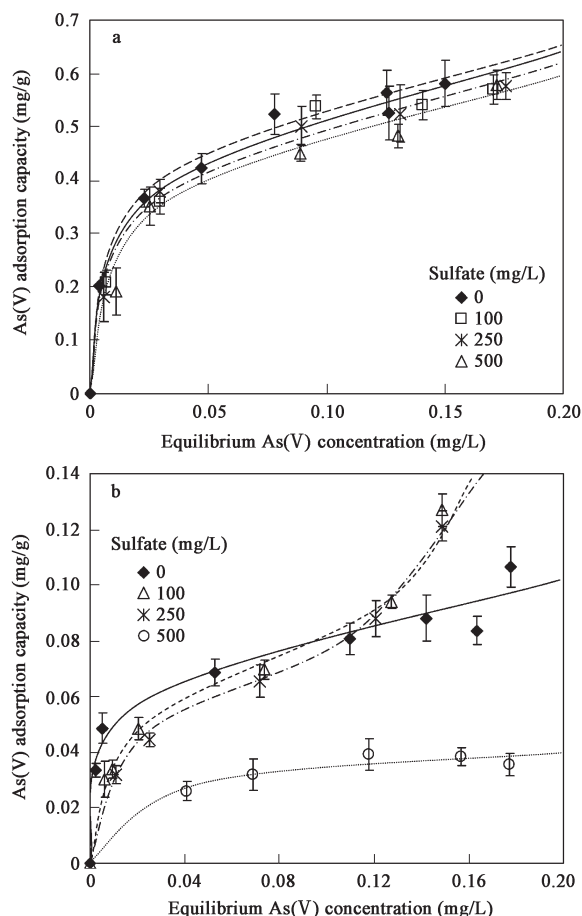


Fig. 2 Adsorption isotherm of As(V) by Fe_2O_3 (a) and Al_2O_3 (b) with the presence of sulfate. Initial As(V) concentration 200 $\mu\text{g/L}$; pH 6 ± 0.1 .

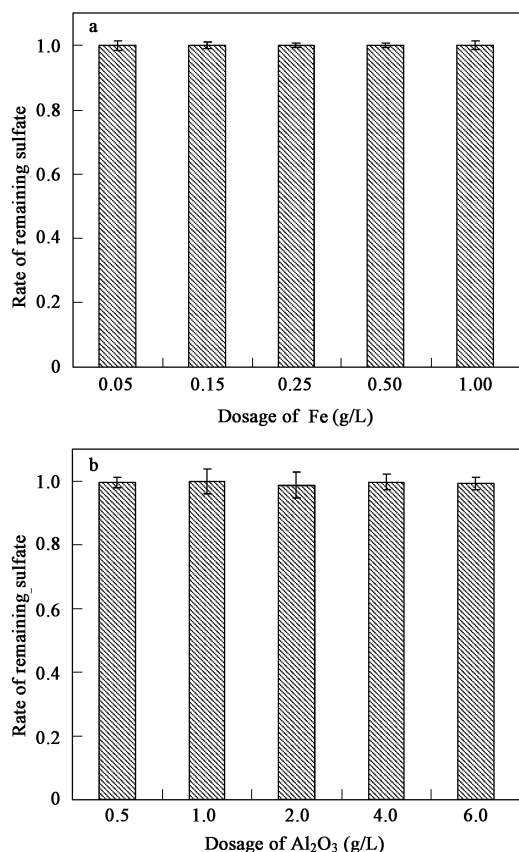


Fig. 3 Comparison of remaining sulfate concentrations after As(V) adsorption with various dosages of Fe₂O₃ (a) and Al₂O₃ (b). Initial sulfate concentration 250 mg/L; pH 6±0.1.

2.2 Sulfate

The As(V) adsorption isotherm curves for Fe₂O₃ and Al₂O₃ within different sulfate environments are shown in Fig.2. Fig.2a demonstrates that the As(V) adsorption isotherm curves were hardly affected by lower concentrations of sulfate; however, the isotherms showed moderate decreasing trends with the increasing of sulfate concentrations, especially at concentrations greater than 250 mg/L. This result is supported by other studies. Meng *et al.* (2000) reported that sulfate with concentrations up to 300 mg/L had no apparent effect on the removal of As(V) with ferric chloride at a pH value of 6.8. They attributed the phenomenon to the fact that the binding affinity between sulfate and ferric hydroxide was much weaker than that between As(V) and ferric hydroxide. Zeng (2004) revealed that the interference of 460 mg/L of sulfate ions on arsenate adsorption with an iron(III)-silica based binary oxide adsorbent was insignificant. Xu *et al.* (1988) stated that sulfate with a high concentration slightly reduced the removal of arsenate with alumina. As presented in Fig.2b, the adsorption of As(V) on Al₂O₃ with a heterogeneous surface (Jeong *et al.*, 2005) is affected by sulfate whose concentrations are relatively higher the initial As(V) concentration. The similar phenomenon was also observed by others such as Balistrieri and Chao (1990).

As shown in Fig.3, the concentration of sulfate after As(V) adsorption on Al₂O₃ remained unchanged from its initial concentration, which is different from those reported

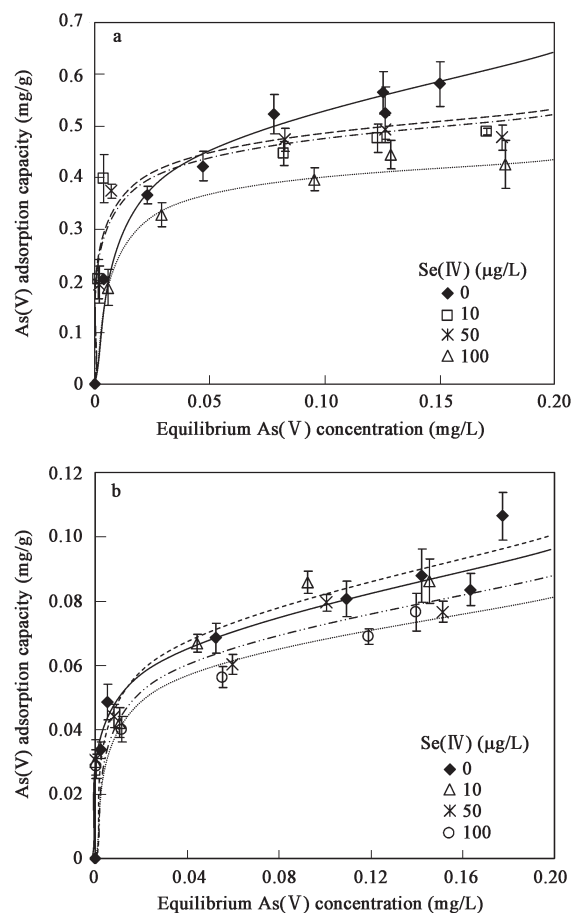


Fig. 4 Adsorption isotherm of As(V) by Fe₂O₃ (a) and Al₂O₃ (b) with the different concentration of Se(IV). Initial As(V) concentration 200 μg/L; pH 6±0.1.

by Wijnja and Schulthess (2000) from their As(V) adsorption tests. They observed through Raman and attenuated total reflectance-Fourier transformed infrared (ATR-FTIR) that both inner- and outer-sphere surface complexes of sulfate ions occur on goethite and aluminum hydroxide surfaces without arsenate anions. By comparing the spectral intensities of sulfate anions on goethite and aluminum oxide, they further revealed that complexation of sulfate anions with aluminum oxide is weaker than that with Fe oxide. Thus, we conclude that the interactions of sulfate ions with surfaces of Fe₂O₃ and Al₂O₃ is weaker those goethite and aluminum hydroxide.

2.3 Selenium

The effects of Se(IV) on As(V) adsorption with Fe₂O₃ and Al₂O₃ are shown in Fig.4. Figs. 4a and 4b show that Se(IV) has larger effect on the adsorption of As(V) with Fe₂O₃ than with Al₂O₃. In addition, as shown in Fig.5, the concentration of Se(IV) after adsorption decreases rapidly with increasing of Fe₂O₃ dosage, while it does slowly with increasing Al₂O₃ dosage. When the initial Se(V) concentration was 50 μg/L, 95% of Se(IV) was adsorbed on the surface of 0.5 g/L Fe₂O₃ added while only 10% of Se(IV) was removed by 0.5 g/L of Al₂O₃.

Our result with Se(IV) is supported by the study of Peak and Sparks (2002). According to Peak and Sparks

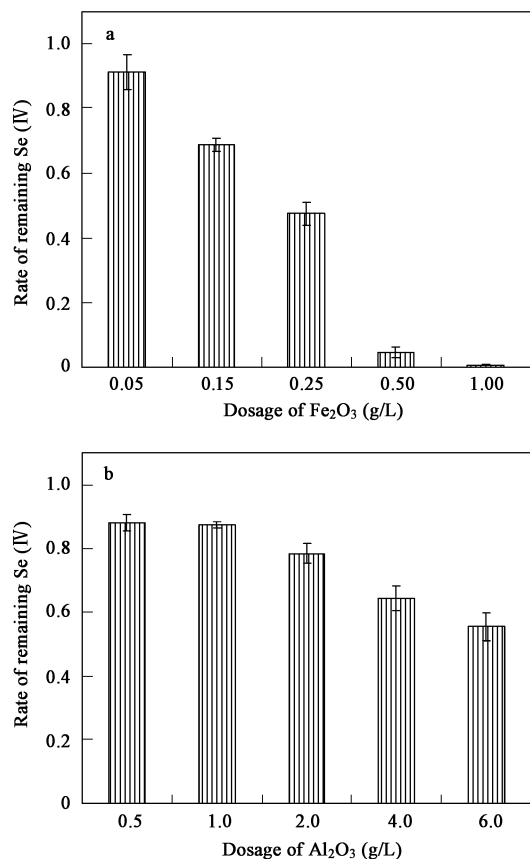


Fig. 5 Comparison of remaining Se(IV) concentrations after As(V) adsorption with various dosages of Fe₂O₃ (a) and Al₂O₃ (b). Initial Se(IV) concentration 50 µg/L; pH 6±0.1.

(2002), selenate ions form inner-sphere and/or outer-sphere surface complexes on surface of iron oxides and hydroxides such as hematite, goethite and hydrous ferric oxide (HFO) under certain pH and ionic strength. Wijnja and Schulthess (2000), using ATR-FTIR spectroscopy, reported that selenate (SeO₄²⁻) ions are adsorbed on goethite and aluminum oxide and that complexation of selenate with iron oxide is stronger than that with aluminum oxide. These results indicate that the binding affinity of As(V) with Fe₂O₃ and Al₂O₃ is stronger than that of selenite, and the complexation of selenite with Fe₂O₃ is stronger than that with Al₂O₃.

2.4 Vanadium

As shown on Fig.6, V(V) slightly affects the As(V) adsorption capacity of Fe₂O₃ but has little effect on that of Al₂O₃. The As(V) adsorption capacity of Fe₂O₃ did not change in the presence of 10 µg/L V(V). Similar results were observed with Al₂O₃ in the presence of 50 µg/L V(V). In high V(V) concentration range (> 50 µg/L), however, the adsorption isotherm curve of As(V) on Fe₂O₃ showed a gradual decrease. It was found that the isotherm curves eventually reach a saturation plateau with the increase of the concentration of V(V) as observed by Lee *et al.* (2004).

Fig.7 indicates that the remaining V(V) concentrations of As(V) solutions decreased significantly with the increasing of dosage of Fe₂O₃. When the initial V(V)

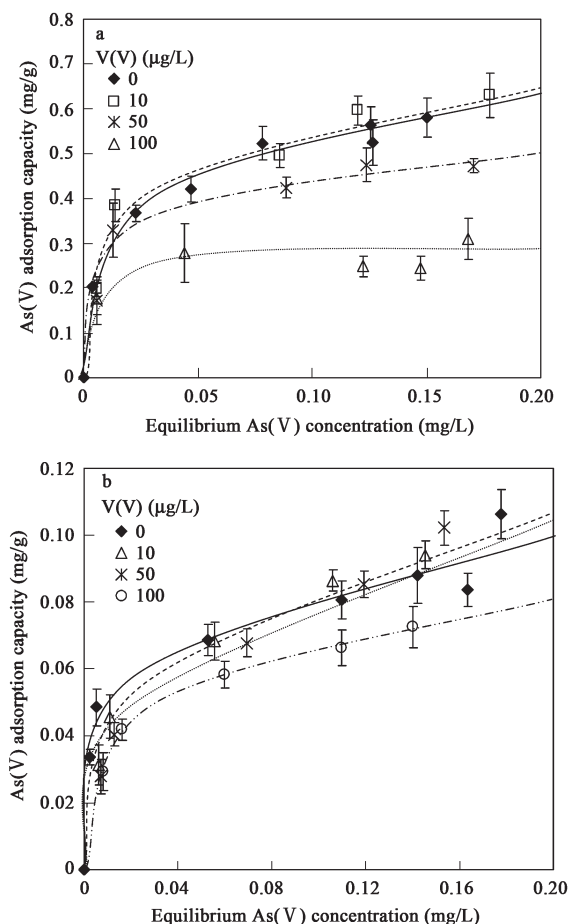


Fig. 6 Adsorption isotherm of As(V) by Fe₂O₃ (a) and Al₂O₃ (b) with different concentrations of V(V). Initial As(V) concentration 200 µg/L; pH 6±0.1.

concentration was a 50 µg/L, Fe₂O₃ and Al₂O₃ adsorb 90% and 10% of V(V), respectively, under the given adsorption conditions. The difference was consistent with the findings of Shieh and Duedall (1988). Golob *et al.* (1971) reported that vanadium (V) can only poorly be adsorbed on activated aluminum oxide. Several investigators discovered that in dilute solutions the principal species of V(V) are mononuclear vanadate oxyanions (VO₂(OH)²⁻ and VO₃(OH)²⁻), which are similar to the behavior of phosphate anions (Wanty and Goldhaber, 1992; Wehrli and Stumm, 1989), and that vanadate oxyanions can adsorb onto the surface of negatively charged iron oxide or clay mineral such as goethite (α -FeOOH) (Cruywagen and Heyns, 1991; Sigg and Stumm, 1980; Peacock and Sherman, 2004) through ligand exchanges. Based on the characteristics of V(V), we can assume that V(V) competes with As(V) for adsorption on the active sites of Fe₂O₃ but the interaction of As(V) with the surface of Fe₂O₃ is still stronger than that of V(V).

2.5 Phosphate

Depending on the pH value, phosphates can present in any of the following four forms in dilute aqueous solution: phosphate ion (PO₄³⁻), hydrogen phosphate ion (HPO₄²⁻), dihydrogen phosphate ion (H₂PO₄⁻), or aqueous phosphoric acid (H₃PO₄(aq)). PO₄³⁻ ions are more

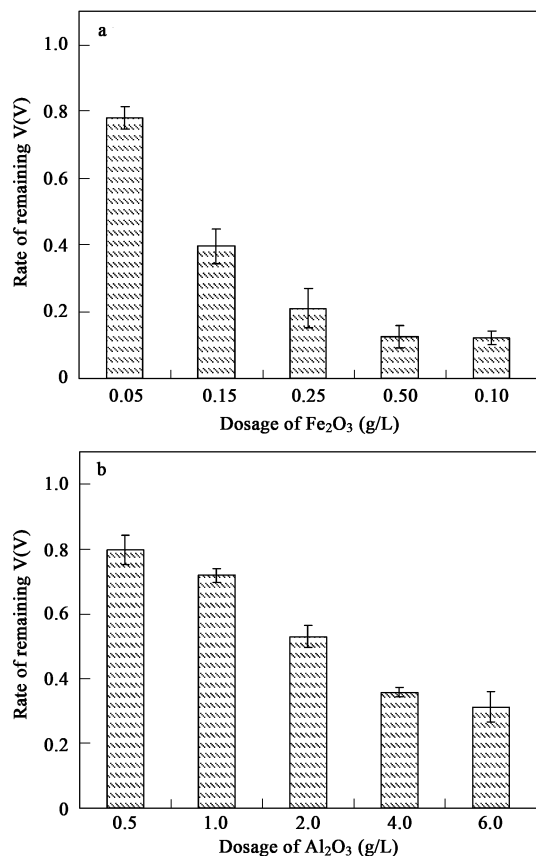


Fig. 7 Comparison of remaining V(V) concentrations after As(V) adsorption with various dosages of Fe₂O₃ (a) and Al₂O₃ (b). Initial V(V) concentration 50 µg/L; pH 6±0.1.

prevalent in strong basic conditions, HPO₄²⁻ ions more likely appear in weak basic conditions. H₂PO₄⁻ ions and aqueous H₃PO₄ predominate in weak and strong acid conditions, respectively (Wikipedia, 2005).

Fig. 8 shows that the increase of phosphate concentration can sharply decrease the As(V) adsorption capacity of Fe₂O₃ and Al₂O₃ even though the trend in low phosphate concentration range is not obvious. The adsorption of As(V) with Al₂O₃ is affected by phosphate to a higher degree than with Fe₂O₃. To achieve the same As(V) adsorption with Al₂O₃ as with Fe₂O₃, higher dosages of Al₂O₃ are required. These results are consistent with several researchers' findings (Meng *et al.*, 2002; Manning and Goldberg, 1996b; Xu *et al.*, 2002). For example, Meng *et al.* (2002) reported that the addition of phosphate (HPO₄²⁻) to water solutions significantly affect the removal of As(V) on iron hydroxides in a over 0.25 mg/L concentration range.

Fig. 9 shows that phosphate anions compete with arsenate ions and adsorb onto Fe₂O₃ and Al₂O₃ in the water. The remaining concentration of phosphate after adsorption decreased significantly with the increase of dosages of Fe₂O₃ and moderately with increase of dosages of Al₂O₃. At initial concentration of 500 µg/L phosphate, 1 g/L of Fe₂O₃ can remove 78% of phosphate, while same dosage of Al₂O₃ adsorbs only 25% of the phosphate anion. This result seems reasonable considering the fact that it is consistent with other researchers' results (Nooney *et al.*,

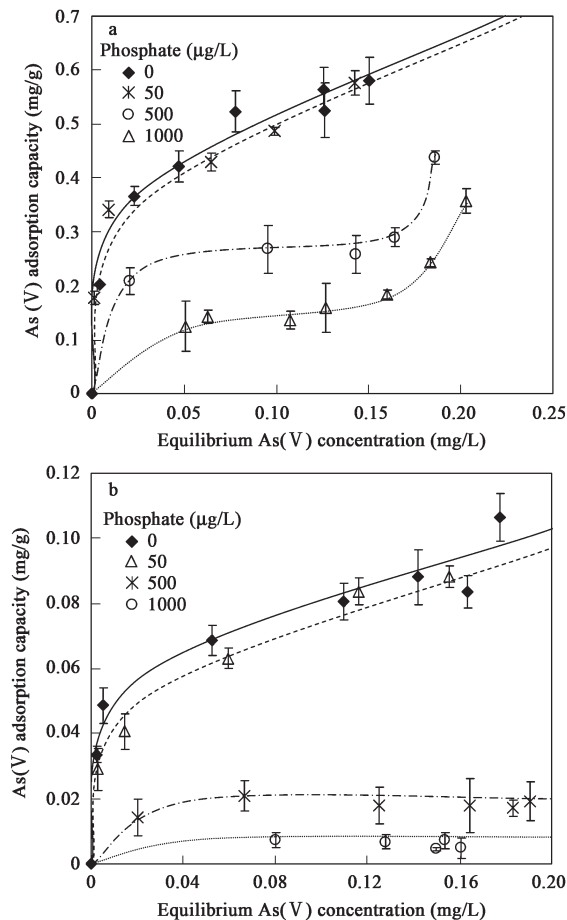


Fig. 8 Adsorption isotherm of As(V) by Fe₂O₃ (a) and Al₂O₃ (b) with different concentrations of phosphate. Initial As(V) concentration 200 µg/L; pH 6±0.1.

1996). Madrid *et al.* (1974) indicated that phosphate ions can easily adsorb onto three kinds of iron oxides (goethite, lipidocrocite, and hematite) at pH 3.2 to 9.6 and they found that the reactions fit well to both Langmuir and Freundlich isotherms. Nooney *et al.* (1996) also found that phosphate uptake was rapid on a thin Fe₂O₃ film of adsorbent in 10 min of exposure time. Javid *et al.* (2004) reported that gibbsite (γ-Al₂O₃) was an effective anion exchange material for phosphate anions at a low pH and that phosphate uptake on γ-Al₂O₃ results from electrostatic interactions (ion exchange) rather than nonelectrostatic adsorption.

Phosphate is very adsorptive on the surfaces of iron and aluminum oxides and has significant effects on the adsorption of arsenic even in low concentration range because of the structural resemblances between arsenic and phosphate ions (Pierce, 1981; Wasay *et al.*, 1996; El Khatib and Balba, 2004). In other words, phosphate can compete with arsenate for binding sites on Fe₂O₃ and Al₂O₃ due to the similarity of their structure. But the complexes of As(V) with Fe₂O₃ and Al₂O₃ should be stronger than those of phosphate according to the findings of Meng *et al.* (2002), which suggest that the constant of binding affinity value of As(V) is seven times greater than that of phosphate on iron hydroxides.

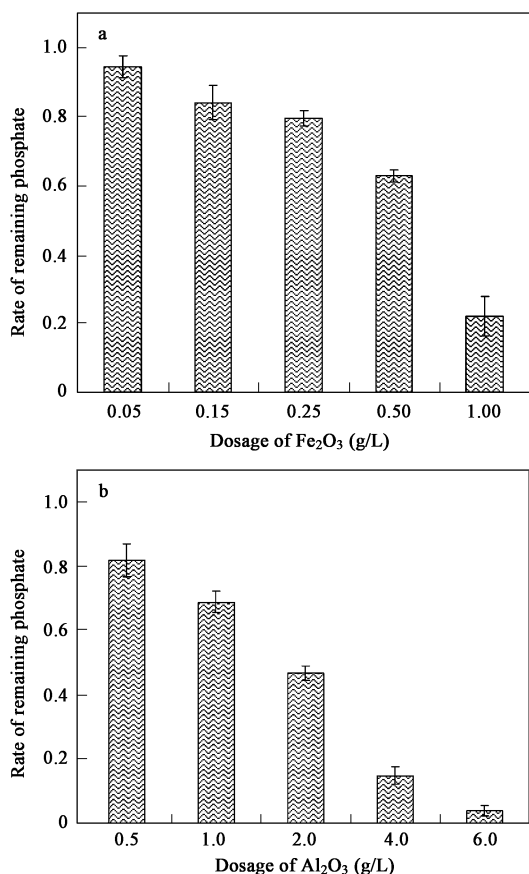


Fig. 9 Comparison of remaining phosphate concentrations after As(V) adsorption with various dosages of Fe₂O₃ (a) and Al₂O₃ (b). Initial phosphate concentration 500 µg/L; pH 6±0.1.

2.6 Silica

The average silica concentration in surface and groundwater is about 14 mg/L (APHA, 1999), therefore, understanding the effect of silica on As(V) adsorption using Fe₂O₃ and Al₂O₃ is important. The changes of As(V) adsorption capacities of Fe₂O₃ and Al₂O₃ with the concentration of silica are shown in Fig. 10. The As(V) adsorption isotherms of Fe₂O₃ and Al₂O₃ show significant decreasing trends when silica concentrations increase. The adsorption of As(V) on Fe₂O₃ at the concentration of 1 mg/L silica increases slightly while that on Al₂O₃ increases are relatively large. We assume that silica with a low concentration may have an enhancing effect on the adsorption of As(V) because of favorable electrostatic effects at the surface of Fe₂O₃ and Al₂O₃ (Wilkie and Hering, 1996). The adsorption of As(V) decreased significantly when silica concentrations increased from 5 to 10 mg/L. The silica solute has higher adverse effects on Al₂O₃ than on Fe₂O₃. These results match those observed by others. Meng *et al.* (2000) reported that with 10 mg/L silicate the removal of As(V) with ferric chloride dropped approximately by 45%, and the As(V) adsorption capacity reduced from 0.96 to 0.27 mg/g Fe. In addition, they suggested that the As(V) adsorption reduction resulted from the strong association of silicate with ferric hydroxide, which reduced the surface sites available for As(V) and increased electrostatic repulsion between As(V) and the negatively charged surface

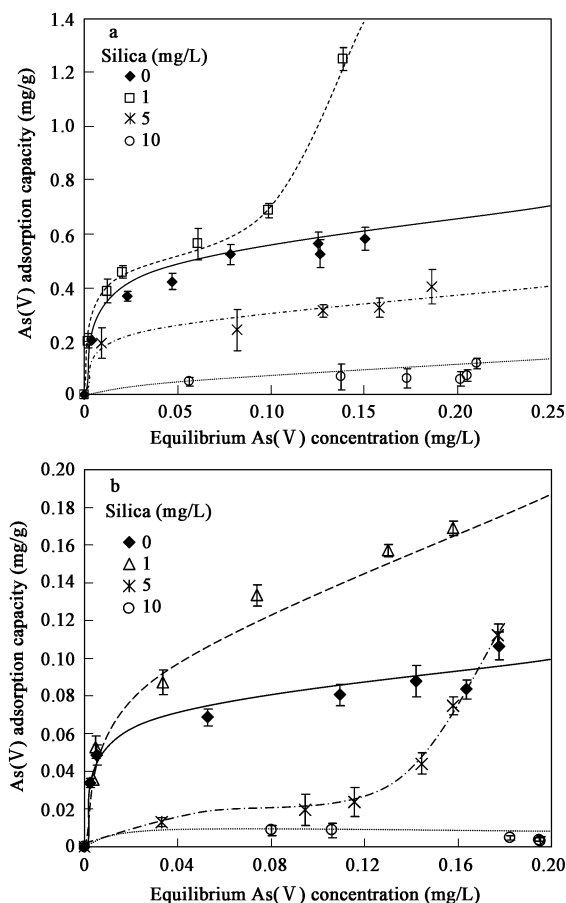


Fig. 10 Adsorption isotherm of As(V) by Fe₂O₃ (a) and Al₂O₃ (b) with different concentrations of silica. Initial As(V) concentration 200 µg/L; pH 6±0.1.

sites. Meng *et al.* (2002) also showed that the adsorption of As(V) on iron hydroxides did not change considerably when the SiO₂ concentrations are lower than 1.4 mg/L because the binding constant of silicate was 800 times lower than that of As(V), but it was obviously affected from 99% to 85% when silica concentrations are higher than 1.5 mg/L. Singh *et al.* (2005) found that the dissolved silicate competes with As(V) in the ferrihydrite-based As(V) coprecipitation and adsorption removal processes, and they proposed that the effect of silicate is to cause a combination of complexation reactions between Fe(III), Si(IV), and As(V) species, and competition between As(V) and Si(IV) for adsorption sites on ferrihydrite.

2.7 Comparison of As(V) adsorption parameters of Fe₂O₃ and Al₂O₃ with the existence of various competing solutes

Table 1 shows the As(V) adsorption parameters of the Langmuir isotherm of Fe₂O₃ and Al₂O₃ within the environment of the studied competing solutes including sulfate, Se(IV), V(V), phosphate, and silica. Under the given test conditions lists in Table 1, the maximum As(V) adsorption capacity (q_{max}) and regression coefficient (R^2) of Langmuir isotherm plot in the absence of competing solutes were observed to be 0.616 mg/g and 0.93 when Fe₂O₃ was used, and 0.098 mg/g and 0.94 when Al₂O₃ was used. In

Table 1 Langmuir adsorption isotherm parameters of As(V) on Fe₂O₃ and Al₂O₃ in the presence of competing solutes

Adsorbents	200 µg/L of As(V) competing solutes	As(V) adsorption parameter		
		* <i>b</i> (L/mg)	* <i>q</i> _{max} (mg/g)	* <i>R</i> ²
Fe ₂ O ₃	No solutes	60.53	0.616	0.93
	Sulfate 250 mg/L	81.33	0.572	0.96
	Selenium(IV) 50 µg/L	32.84	0.503	0.95
	Vanadium(V) 50 µg/L	91.49	0.521	0.96
	Phosphate 500 µg/L	82.56	0.327	0.59
	Silica 5 mg/L	145.58	0.327	0.74
Al ₂ O ₃	No solutes	44.56	0.098	0.94
	Sulfate 250 mg/L	50.31	0.087	0.96
	Selenium(IV) 50 µg/L	7.06	0.076	0.87
	Vanadium(V) 50 µg/L	55.19	0.098	0.89
	Phosphate 500 µg/L	154.98	0.019	0.61
	Silica 5 mg/L	11.86	0.045	0.82

Conditions: initial As(V) concentration 200 µg/L, pH 6±0.1. **b* and *q*_{max} are the two parameters in Langmuir adsorption isothermal equation shown as: $\frac{1}{q_e} = \frac{1}{q_{\max} b C_e} + \frac{1}{q_{\max}}$, where *b* is a constant, *q*_{max} represents the maximum adsorption capacity of the adsorbent; *R*² is the regression coefficient of 1/*q*_e-1/*C*_e plot.

the presence of phosphate at 500 µg/L concentration, the adsorption capacity (*q*_{max}) and the regression coefficient (*R*²) of Langmuir isotherm plot were reduced to 0.327 mg/g and 0.59 when Fe₂O₃ was used, and 0.019 mg/g and 0.61 when Al₂O₃ was used. Addition of 5 mg/L silica to arsenic solution reduced the values of *q*_{max} and *R*², respectively, to 0.327 mg/g and 0.74 when Fe₂O₃ was used, and respectively, to 0.045 mg/g and 0.82 when Al₂O₃ was used. Considering the adsorption bond strength, *b*, selenite ion bonds on Fe₂O₃ and Al₂O₃ were much weaker than those of the other competing solutes. Silica ion bonds are stronger than the others on Fe₂O₃, while phosphate ion bonds are much stronger than the others on Al₂O₃. These results show that effects of competing solutes including phosphate and silica on adsorption of arsenic with Fe₂O₃ are less significant than with Al₂O₃.

Therefore, based on the lower concentration level of phosphate compared with other competing solutes, and the values of the adsorption capacity and regression coefficient (*R*²) of Langmuir isotherm plots discussed above, phosphate anions are found to be the most prominent solute competing against As(V) for adsorption on Fe₂O₃ and Al₂O₃. With the values of adsorption capacity and dosages considered, Fe₂O₃ is found to be a better adsorbent than Al₂O₃ for removing As(V) in the presence of competing solutes in water.

3 Conclusions

Different competing solutes have different effects on the adsorption of As(V) with Fe₂O₃ and Al₂O₃. Chloride and nitrate anions do not show notable effects on the adsorption of As(V) with Fe₂O₃ and Al₂O₃. Sulfate anions have moderate adverse effects on the adsorption of As(V) with Al₂O₃ while they do not have considerable effects on the adsorption of As(V) with Fe₂O₃. The stronger complexes formed between Se(IV) and V(V) with Fe₂O₃ than with Al₂O₃ make the adsorption of As(V) with Fe₂O₃ more significantly affected than with Al₂O₃. The most significant interference with the removal of As(V) by Fe₂O₃ and Al₂O₃ occurs in the presence of phosphate and silica solutes. Generally speaking, Fe₂O₃ has a better

performance than Al₂O₃ in adsorbing As(V) when the studied competing ions exist in As(V) solutions although both materials can reduce the level of As(V) in water to the level lower than that required by WHO and USEPA.

Acknowledgements

This research was supported in part by the Busan Metropolitan Water Works in Korea.

References

- Anderson M A, Ferguson J F, Gavis J, 1976. Arsenate adsorption on amorphous aluminum hydroxide[J]. Journal of Colloid and Interface Science, 54(3): 391–399.
- APHA, AWWA, WEF, 1998. Standard methods for the examination of water and wastewater[S]. 20th ed. Washington DC, USA: APHA.
- Balistreri L S, Chao T T, 1990. Adsorption of selenium by amorphous iron oxyhydroxide and manganese dioxide[J]. Geochimica et Cosmochimica Acta, 54(3): 739–751.
- Brookins D G, 1988. Eh-pH diagrams for geochemistry[M]. Berlin, Germany: Springer-Verlag.
- Buchanan W D, 1962. Toxicity of arsenic compounds[M]. New York, USA: Elsevier Publishing Company.
- Cruywagen J J, Heyns J B, 1991. Vanadium(V) equilibria. Spectrophotometric and enthalpimetric investigation of the dimerization and deprotonation of HVO₄²⁻[J]. Polyhedron, 10(2), 249–253.
- Davis S A, Misra M, 1997. Transport model for the adsorption of oxyanions of selenium(IV) and arsenic(V) from water onto lanthanum- and aluminum-based oxides[J]. Journal of Colloid and Interface Science, 188(2): 340–350.
- Dixit S, Hering J G, 2003. Comparison of arsenic(V) and arsenic(III) sorption onto iron oxide minerals: Implications for arsenic mobility[J]. Environ Sci Technol, 37(18): 4182–4189.
- El Khatib E A, Balba A M, 2004. Arsenate chemistry in soils of arid ecosystems[J]. Alexandria Science Exchange, 25(1), 229–261.
- Ferguson J F, Gavis J, 1972. Review of the arsenic cycle in natural waters[J]. Water Research, 6: 1259–1274.
- Frank P, Clifford D, 1986. As(III) oxidation and removal from drinking water[S]. USEPA Proj Summary 600/S2-86/021.
- Goldberg S, Johnston C T, 2001. Mechanisms of arsenic adsorption on amorphous oxides evaluated using macroscopic

- measurements, vibrational spectroscopy, and surface complexation modeling[J]. *Journal of Colloid and Interface Science*, 234(1), 204–216.
- Golob J, Kosta L, Modic R, 1971. Adsorption separation of vanadium from arsenic, phosphorus, and fluorine by activated aluminum oxide[J]. *Vestnik Slovenskega Kemijskega Društva*, 18(1-4): 21–25.
- Heinz Center, USGS (US Geological Survey), 2000. Summary of nutrient concentrations for streams and ground water[EB]. <http://water.usgs.gov/nawqa/nutrients/datasets/nutconc2000/>, accessed May 10, 2005.
- Hug S, von Guten M W, Leupin O, 2005. Options for safe drinking water at the household level[EB]. http://www.eawag.ch/research_e/w+t/ags/websoras/hauptframe.html, accessed December 29, 2004.
- Jain A, Loeppert R H, 2000. Effect of competing anions on the adsorption of arsenate and arsenite by ferrihydrite[J]. *Journal of Environmental Quality*, 29(5): 1422–1430.
- Javid M, Mustafa S, Gul R *et al.*, 2004. Sorption/desorption properties of γ -Al₂O₃ towards phosphate anions[J]. *Journal of the Chemical Society of Pakistan*, 26(2): 116–119.
- Jeong Y, Fan M, Li N *et al.*, 2005. The adsorption of arsenic(V) by iron and aluminum oxides[D]. Ph. D Dissertation, Iowa State University, USA.
- Klaassen C D, 1996. Casarett and doull's toxicology—the basic science of poisons[M]. 5th ed. New York: McGraw-Hill.
- LANL (Los Alamos National Laboratory), 2004. Arsenic(2004)[EB]. <http://pearl1.lanl.gov/periodic/>, last visited July 10, 2005.
- Lee B W, De Haan M, Reddy S *et al.*, 2004. Evaluation of EBCT on arsenic adsorption performance and competitive preloading[C]. Proceedings, AWWA Water Quality Technology Conference and Exhibition.
- Madrid L, Cabrera P, De Arambarri P *et al.*, 1974. Determination of the isosteric heat and considerations on the mechanism of adsorption of phosphate by iron oxides[J]. *Anales de Edafologia y Agrobiologia*, 33(9/10): 755–765.
- Manning B A, Goldberg S, 1996a. Modeling arsenate competitive adsorption on kaolinite, montmorillonite and illite[J]. *Clays and Clay Minerals*, 44(5): 609–623.
- Manning B A, Goldberg S, 1996b. Modeling competitive adsorption of arsenate with phosphate and molybdate on oxide minerals[J]. *Soil Science Society of America Journal*, 60(1): 121–131.
- Meng X, Bang S, Korfiatis G P, 2000. Effects of silicate, sulfate, and carbonate on arsenic removal by ferric chloride[J]. *Water Research*, 34(4): 1255–1261.
- Meng X, Korfiatis G P, Bang S *et al.*, 2002. Combined effects of anions on arsenic removal by iron hydroxides[J]. *Toxicology Letters*, 133(1): 103–111.
- Nooney M G, Murrell T S, Corneille J S *et al.*, 1996. A spectroscopic investigation of phosphate adsorption onto iron oxides[J]. *Journal of Vacuum Science and Technology, A: Vacuum, Surfaces, and Films*, 14(3): 1357–1361.
- Oscarson D W, Huang P M, Liaw W K *et al.*, 1983. Kinetics of oxidation of arsenite by various manganese dioxides[J]. *Soil Science Society of America Journal*, 47(4): 644–648.
- Peacock C L, Sherman D M, 2004. Vanadium(V) adsorption onto goethite (α -FeOOH) at pH 1.5 to 12: A surface complexation model based on ab initio molecular geometries and EXAFS spectroscopy[J]. *Geochimica et Cosmochimica Acta*, 68(8): 1723–1733.
- Peak D, Sparks D L, 2002. Mechanisms of selenate adsorption on iron oxides and hydroxides[J]. *Environ Sci Technol*, 36(7): 1460–1466.
- Pierce M L, 1981. Chemocal modeling of arsenic in aqueous systems[D]. Ph. D Thesis, Arizona State University, USA.
- Pierce M L, Moore C B, 1982. Adsorption of arsenite and arsenate on amorphous iron hydroxide[J]. *Water Research*, 16(7): 1247–1253.
- Raven K P, Jain A, Loeppert R H, 1998. Arsenite and arsenate adsorption on ferrihydrite: kinetics, equilibrium, and adsorption envelopes[J]. *Environ Sci Technol*, 32(3): 344–349.
- Reynolds J G, Naylor D V, Fendorf S E, 1999. Arsenic sorption in phosphate-amended soils during flooding and subsequent aeration[J]. *Soil Science Society of America Journal*, 63(5): 1149–1156.
- Roberts L C, Hug S J, Ruettimann T *et al.*, 2004. Arsenic removal with iron(II) and iron(III) in waters with high silicate and phosphate concentrations[J]. *Environ Sci Technol*, 38(1): 307–315.
- Rosenblum E, Clifford D, 1983. Equilibrium arsenic capacity of activated alumina[S]. EPA-600/2-83-107. 89.
- Safullah S, Kabir A, Hasan K *et al.*, 2004. Comparative study of adsorption-desorption of arsenic on various arsenic removing materials[J]. *Journal of Bangladesh Academy of Sciences*, 28(1): 27–34.
- Shieh C S, Duedall I W, 1988. Role of amorphous ferric oxyhydroxide in removal of anthropogenic vanadium from seawater[J]. *Marine Chemistry*, 25(2): 121–139.
- Sigg L, Stumm W, 1980. The interactions of anions and weak acids with the hydrous goethite (α -FeOOH) surface[J]. *Colloids and Surfaces*, 2: 101–117.
- Singh P, Zhang W, Muir D M *et al.*, 2005. The effect of silicate on the adsorption of arsenate on coprecipitated ferrihydrite[C]. Proceedings of Symposium held during the TMS Annual Meeting, San Francisco, CA, United States. 129–135.
- Stumm W, Morgan J J, 1996. Aquatic chemistry, chemical equilibria and rates in natural waters[M]. 3rd ed. New York, USA: John Wiley & Sons.
- Thirunavukkarasu O S, Viraraghavan T, Subramanian K S, 2003. Arsenic removal from drinking water using granular ferric hydroxide[J]. *Water SA*, 29(2): 161–170.
- Tseng W P, Chu H M, How S W *et al.*, 1968. Prevalence of skin cancer in an endemic area of chronic arsenicism in Taiwan[J]. *Journal of the National Cancer Institute*, 40(3): 453–463.
- USEPA (US Environmental Protection Agency), 1999a. Maximum contaminant levels and health advisory levels[EB]. <http://www.epa.gov/safewater/uic/classw/pdfs/appd.pdf>, accessed May 28, 2005.
- USEPA, 1999b. Microbial and disinfection byproduct rules simultaneous compliance guidance manual[EB]. [EPA 815-R-99-015]. <http://www.epa.gov/safewater/mdbp/simult.pdf>, last visited September 31, 2005.
- USEPA, 2001a. Arsenic rule benefits analysis: An Sab review[EB]. [EPA-SAB-RSAC-01-005.]. Washington, DC.
- USEPA, 2001b. National primary drinking water regulations[EB]. <http://www.epa.gov/safewater/mcl.html#mcls> 2001, last visited July 23, 2004.
- Wanty R B, Goldhaber M B, 1992. Thermodynamics and kinetics of reactions involving vanadium in natural systems: Accumulation of vanadium in sedimentary rocks[J]. *Geochimica et Cosmochimica Acta*, 56: 1471–1483.
- Wasay S A, Tokunaga S, Park S W, 1996. Removal of hazardous anions from aqueous solutions by La(III)- and Y(III)-impregnated alumina[J]. *Separation Science and*

- Technology, 31(10): 1501–1514.
- Wehrli B, Stumm W, 1989. Vanadyl in natural waters: Adsorption and hydrolysis promote oxygenation[J]. *Geochimica et Cosmochimica Acta*, 53: 69–77.
- Welch A H, Lico M S, Hughes J L, 1988. Arsenic in ground water of the western United States[J]. *Ground Water*, 26(3): 333–347.
- WHO (World Health Organization), 2001. Arsenic in drinking water[EB]. <http://www.who.int/mediacentre/factsheets/fs210/en/>, last visited August 12, 2004.
- Wijnja H, Schulthess C P, 2000. Vibrational spectroscopy study of selenate and sulfate adsorption mechanisms on Fe and Al (Hydr)oxide surfaces[J]. *Journal of Colloid and Interface Science*, 229(1): 286–297.
- Wikipedia, 2005. Phosphate[EB]. <http://en.wikipedia.org/wiki/Phosphate>, last visited October 10, 2004.
- Wilkie J A, Hering J G, 1996. Adsorption of arsenic onto hydrous ferric oxide: effects of adsorbate/adsorbent ratios and co-occurring solutes[J]. *Colloids and Surfaces, A: Physicochemical and Engineering Aspects*, 107: 97–110.
- Xu H, Allard B, Grimvall A, 1988. Influence of pH and organic substance on the adsorption of As(V) on geologic materials[J]. *Water Air and Soil Pollution*, 40: 293–305.
- Xu Y, Nakajima T, Ohki A, 2002. Adsorption and removal of arsenic(V) from drinking water by aluminum-loaded Shirasu-zeolite[J]. *Journal of Hazardous Materials*, 92(3): 275–287.
- Yean S, Cong L, Kan A *et al.*, 2005. Sorption/desorption of arsenic to magnetite nanoparticles[C]. Abstracts of Papers, 229th ACS National Meeting, San Diego, CA, United States, March 13–17.
- Zeng L, 2004. Arsenic adsorption from aqueous solutions on an Fe(III)-Si binary oxide adsorbent[J]. *Water Quality Research Journal of Canada*, 39(3): 267–275.
- Zhang W, Singh P, Paling E *et al.*, 2004. Arsenic removal from contaminated water by natural iron ores[J]. *Minerals Engineering*, 17(4): 517–524.
- Zhang J, Stanforth R, 2005. Slow adsorption reaction between arsenic species and goethite (α -FeOOH): Diffusion or heterogeneous surface reaction control[J]. *Langmuir*, 21(7): 2895–2901.